

# Investigation of the Ni(II) Adsorption, in Respect to Kinetics and Thermodynamics, by Carbonized Walnut Shell from Aqueous Solution

Bircan Köse, Saliha Erentürk

**Abstract**— The objective in this study was to investigate the adsorption, in terms of reaction speed and thermodynamics, of the Ni(II) from aqueous solution. Carbonized walnut shell was used as an adsorbent. The effect of contact time (0-90min) and temperatures (26-45°C) on the adsorption properties have been studied. The adsorption process follows the pseudo-second-order kinetic model very well. The thermodynamic parameters, such as Gibb's free energy change ( $\Delta G^\circ$ ), standard enthalpy change ( $\Delta H^\circ$ ) and standard entropy change ( $\Delta S^\circ$ ) were also evaluated. The thermodynamic parameters ( $\Delta G^\circ < 0$ ,  $\Delta S = -17.37$  J/mol/K,  $\Delta H^\circ = -5.72$  kJ/mol) indicated that it was a spontaneously exothermic reaction.

**Index Terms**— Adsorption, Kinetics, Ni (II), Thermodynamics, Walnut Shell.

## I. INTRODUCTION

Agricultural and industrial developments have been increased with scientific and technological progress throughout the world in recent years. These developments have caused the release of various pollutants especially heavy metals into the water source, which threaten and hazard for all living organisms in the ecosystem. Heavy metals such as lead, copper, cadmium, zinc and nickel are among the most common pollutants in the water [1]. Among these metals, nickel is in wide demand in different industries such as batteries, mineral processing, electroplating, smelting, coin, paint formulation etc. [2],[3]. Nickel is among the non-biodegradable toxic heavy metals and at high concentrations Ni(II) is known to cause different types of diseases such as headache, pulmonary fibrosis, nausea and vomiting, chest pain, tightness of the chest, dry cough and shortness of breath, rapid respiration, cyanosis, renal edema and skin dermatitis and extreme weakness [4-7]. Therefore, it is necessary to remove Ni(II) from the water. For this purpose, there are various methods to solve this problem such as chemical precipitation, ionic exchange, filtration, electrochemical treatment, membrane techniques, recovery by evaporation and adsorption [8], [9]. The adsorption methods is used commonly because it is both economically favorable and technically applicable than other methods [10]. In this study the adsorption of Ni(II) on the adsorbent prepared from walnut shell has been investigated under different environmental conditions. Kinetic data have been analyzed by pseudo-first and pseudo-second order models to

obtain the kinetic constants and also thermodynamic study of Ni(II) removal has been conducted.

## II. MATERIAL AND METHOD

### A. Preparation of Adsorbent

The adsorbent was prepared from walnut shell. The plant was first broken and then carbonized in the oven which was heated from the ambient temperature to the 500°C with the heating rate of 10°C/min for 90 minutes. During the carbonization process nitrogen was fed to furnace at a flow rate of 58 L/h. After the carbonization was completed, sample removed from the oven was first grinded and then sieved down to 0.092-0.063 mm.

### B. Experimental

Adsorption studies were carried out by 200 mL solutions prepared at the desired concentration that obtained by diluting from the 1000 mg/L Ni(II) stock. In the experiments a thermostatic incubator shaker with a shaking speed of 200 rpm was used. During the experiments initial Ni(II) concentration 20 mg/L, adsorbent dosage 0.4 g/L and pH of 6 were selected as constant while temperatures selected varied between 26, 37, 45°C. Samples obtained between 1-90 min. were filtered to obtain clear solutions. The concentration of the residual Ni(II) in the solution was measured by Atomic Absorption spectrophotometer (Shimadzu AA-670).

## III. RESULTS AND DISCUSSION

### A. Kinetic studies

In order to determine the rate of Ni(II) removal from the solutions, kinetic studies were evaluated. Kinetic models were examined to explain the kinetics of Ni(II) adsorption on the CWS by using pseudo first-order and pseudo second-order [9]. The correlation coefficient ( $R^2$ ) was selected for expressing the conformity between experimental data and the model predicted. The  $R^2$  values approaching to 1 indicates the best fitting between the data obtained from the kinetic model and by the experimentally.

### B. The pseudo first-order model

The pseudo first-order equation is generally presented as follows;


$$\log(q_e - q_t) = \log(q_e) - \frac{k_1}{2.303} t \quad (1)$$

Bircan Köse, Department of Chemical Engineering, Faculty of Engineering/ University of Atatürk/ Erzurum, Turkey

Saliha Erentürk\* Department of Chemical Engineering, Faculty of Engineering/ University of Atatürk/ Erzurum, Turkey,

## Investigation of the Ni(II) Adsorption, in Respect to Kinetics and Thermodynamics, by Carbonized Walnut Shell from Aqueous Solution

where  $q_e$  ( $\text{mg g}^{-1}$ ) and  $q_t$  ( $\text{mg g}^{-1}$ ) are the adsorption capacity at equilibrium and at time  $t$  (min), respectively,  $k_1$  is the rate coefficient of pseudo first-order adsorption ( $\text{L min}^{-1}$ ). The plot of  $\log(q_e - q_t)$  vs.  $t$  was shown in Figure 1. From the Figure 1,  $k_1$  can be determined from the slope of linear line and also  $q_e$  can be determined from the intercept of the plot [11].

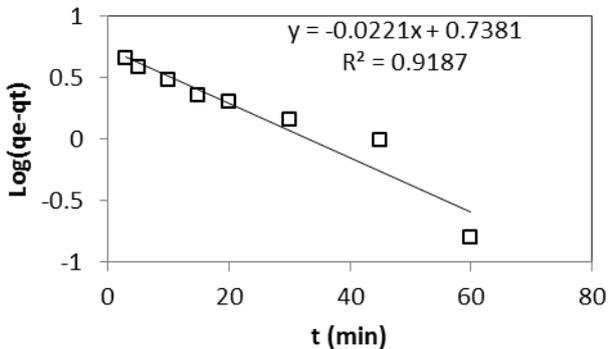


**Figure 1.** Pseudo first order kinetics model of Ni(II) removal by CWS

### C. The pseudo second-order model

The pseudo second-order adsorption kinetic rate equation is expressed as:

$$\frac{t}{q_t} = \frac{t}{q_e} + \frac{1}{k_2 q_e^2} \quad (2)$$

where  $k_2$  is the rate coefficient of pseudo second-order adsorption ( $\text{g mg}^{-1} \text{min}^{-1}$ ). The plot of  $t/q_t$  vs  $t$  illustrated in Figure 2. From the Figure 2,  $q_e$  can be determined from the slope of linear line and also  $k_2$  can be determined from the intercept of the plot [11].

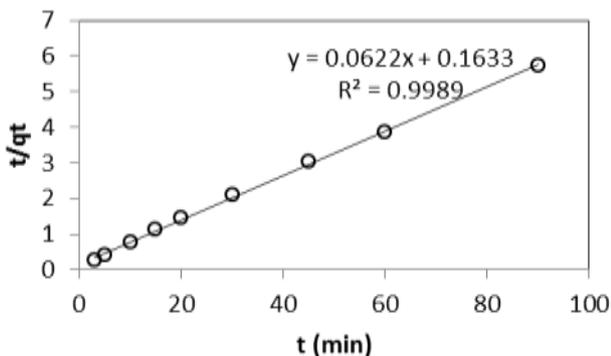

**Figure 2.** Pseudo second order kinetics model of Ni(II) removal by CWS


Kinetic model parameters obtained were given in Table 1. The obtained correlation coefficient values of  $R^2$  for pseudo second-order expression, and pseudo-first order were 0.999, 0.919 respectively. It is obvious that the correlation coefficient  $R^2$  of pseudo second-order expression was higher than that of pseudo-first order expression. The adsorption of Ni(II) onto CWS was represented by the pseudo-second-order kinetic model. Similar results have been reported by Wang and Li, 2009 for nonliving biomass of the marine brown alga laminaria japonica, by [12] for calcium alginate, by [13] for blank alginate beads.

**Table 1.** Adsorption rate constants associated with pseudo first and second order kinetic models.

	$q_{e,\text{experimental}}$ ( $\text{mg g}^{-1}$ )	$R^2$	$q_{e,\text{calculated}}$ ( $\text{mg g}^{-1}$ )	$k_1$ $\text{L min}^{-1}$
Pseudo first-order kinetic model	15.748	0.968	5.471	0.051
	$q_{e,\text{experimental}}$ ( $\text{mg g}^{-1}$ )	$R^2$	$q_{e,\text{calculated}}$ ( $\text{mg g}^{-1}$ )	$k_2$ $\text{g mg}^{-1} \text{min}^{-1}$
Pseudo second-order kinetic model	15.748	0.999	16.088	0.025

### D. Thermodynamic study

The effect of temperature on Ni(II) adsorption was investigated at the temperature range of 26–45°C and was illustrated in Figure 3. It was seen from the Figure that percentage removal of Ni(II) increased with increasing temperature from 26–45°C, which indicates that adsorption of Ni(II) onto the surface of CWS was exothermic.

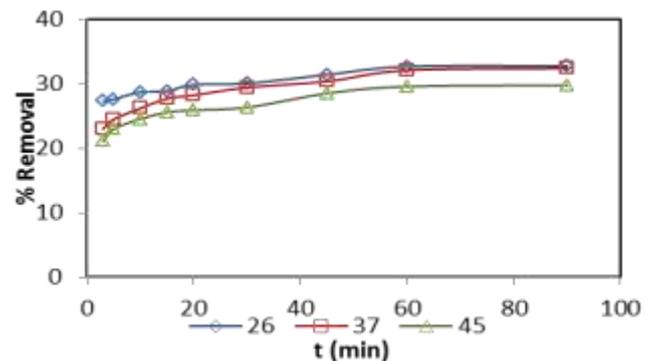

**Figure 3.** Effect of temperature on removal of Ni(II) (adsorbent dosage 0.4 g/L, initial concentration 20 mg/L, pH 6)

Thermodynamic parameters such as enthalpy ( $\Delta H^\circ$ ), entropy ( $\Delta S^\circ$ ), and Gibbs free energy, ( $\Delta G^\circ$ ) for Ni(II) adsorption onto CWS were obtained. These parameters describe whether the adsorption is endothermic or exothermic, and also spontaneously of the adsorption process. The Gibbs free energy ( $\Delta G^\circ$ ) of the adsorption is given by the following equation:

$$\Delta G^\circ = -RT \ln K_d \quad (3)$$

where  $K_d$  is the distribution coefficient,  $R$  ( $8.314 \text{ J mol}^{-1} \text{ K}^{-1}$ ) is the gas constant and  $T$  is the absolute temperature (K) (Ding et al. 2013). The adsorption distribution coefficient ( $K_d$ ) can be calculated from:

$$K_d = \frac{q_e}{c_e} \quad (4)$$

where  $q_e$  is adsorption capacity at equilibrium, and is obtained by the following equation

$$q_e = \frac{(C_0 - C_e) \times V}{m} \quad (5)$$

where  $C_0$  and  $C_e$  are the initial and equilibrium concentrations of Ni(II) ion in solution ( $\text{mg/L}$ ).  $m$  is the mass of carbon sample (g),  $V$  is the volume of adsorption solution (L). The value of the distribution coefficient ( $K_d$ ) for the adsorption of Ni(II) ion on the adsorbent were calculated at different

temperature and at equilibrium time using Eqs. (4) and (5). The amounts of  $\Delta H^\circ$  and  $\Delta S^\circ$  can be determined from the slope and intercept of the straight line obtained from plotting  $\ln K_d$  vs  $1/T$  using Eq (6) which was shown in Figure 4 [14].

$$\ln K_d = \frac{\Delta S^\circ}{R} - \frac{\Delta H^\circ}{RT} \quad (6)$$

After obtaining  $\Delta H^\circ$  and  $\Delta S^\circ$  values of the adsorption,  $\Delta G^\circ$  for the examined temperature was calculated from the following equation:

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (7)$$

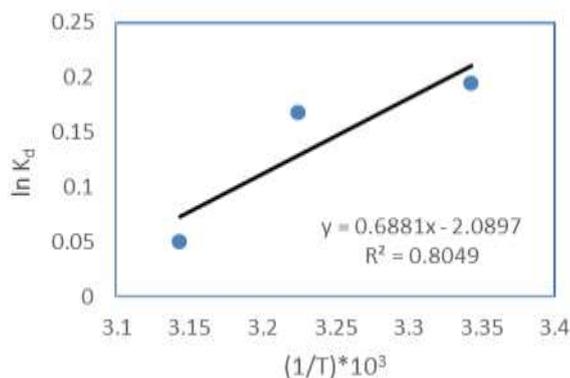


Figure 4. Adsorption thermodynamics.

Table 2. Thermodynamic parameters for the adsorption of Ni(II)

T <sup>o</sup> C	K <sub>d</sub>	ΔG <sup>o</sup> kJ mol <sup>-1</sup>	ΔS <sup>o</sup> jmol <sup>-1</sup> K <sup>-1</sup>	ΔH <sup>o</sup> kJ mol <sup>-1</sup>
26	1.22	-0.52		
37	1.18	-0.33	-17.37	-5.72
45	1.05	-0.19		

All the thermodynamic parameters were listed in Table 2. As the  $\Delta G$  values were negative it can be said that the adsorption process of Ni(II) was spontaneous under the studied conditions. The values of  $\Delta G^\circ$  increased from -0.52 to -0.19 kJ/mol in the temperature range of 26–45°C. The negative value of enthalpy change ( $\Delta H^\circ$ ) obtained for Ni(II) adsorption, illustrates the exothermic nature of the reaction. Some authors such as [15-17] have reported similar results.

#### IV. CONCLUSIONS

This study highlights the potential of CWS usage as an adsorbent for the removal of Ni(II) from solutions. The adsorption of Ni(II) on CWS was represented by the pseudo-second-order kinetic model. Adsorption thermodynamic showed that the adsorption process was exothermic and spontaneous.

#### ACKNOWLEDGMENT

This work was supported by the Atatürk University Research Foundation (BAP, 2013/108)

#### REFERENCES

- [1] S. E. Samra, B. Jeragh, A. M. EL-Nokrashy and A. A. El-Asmy "Adsorption and thermodynamics of lead (II) using seeds of watermelon (SWM) as a low cost sorbent," *International Journal of Engineering and Applied Sciences (IJEAS)* ISSN: 2394-3661, Vol-1, Issue-1, October 2014.
- [2] Z. V. P. Murthy, K. Vijayaragavan and K. K. Pant, "Kinetic and Thermodynamic Studies of Ni(II) Adsorption onto Activated Carbon of *Abelmoschus manihot* from Aqueous Solutions," *Journal of Dispersion Science and Technology*, 34: 2013, 923–931.
- [3] B. Liao, W. Sun, N. Guo, S.I. Ding and S. Su, "Equilibriums and kinetics studies for adsorption of Ni(II) ion on chitosan and its triethylenetetramine derivative," *Colloids and Surfaces A: Physicochemical and Engineering Aspects*. 501: 2016, 32–41.
- [4] Ademiluyi F.T, and Nwanam Rodney "Effect of Process Parameters on the Single Adsorption of Zinc and Nickel ions Using Activated Carbon from Waste Nigerian Bamboo," *International Journal of Engineering and Applied Sciences (IJEAS)* ISSN: 2394-3661, Vol-3, Issue-1, January 2016.
- [5] U.S. Environmental Protection Agency. Health Assessment Document for Nickel. EPA/600/8-83/012F. National Center for Environmental Assessment, Office of Research and Development, Washington, DC. 1986.
- [6] E. Malkoc and Y. Nuhoglu, Y., "Investigations of Ni(II) removal from aqueous solutions using tea factory waste," *J Hazard Mater* 127: 2005,120–128.
- [7] E. Malkoc and Y. Nuhoglu, Y., Thermodynamic and kinetic studies for environmentally friendly Ni(II) biosorption using waste pomace of olive oil factory," *Bioresour Technol* Vol-100, Issue 8, April 2009, pp. 2375-2380
- [8] S. Basha, Z. V. P. Murthy and B. Jha, "Sorptions of Hg(II) onto Carica papaya: experimental studies and design of batch sorber," *Chem. Eng. J.* 147:2009, 226–234.
- [9] B. Köse and S. Erentürk, "Removal of Pb(II) from water by carbonized walnut shell: characterization of adsorbent, adsorption capacity, kinetic, thermodynamic and isotherm studies," *Desalin. Water Treat.* 60 (2017) 301–309
- [10]. C. L. Hsueh, Y. W. Lu, C. C. Hung, Y. H. Huang and C. Y. Chen, "Adsorption kinetic, thermodynamic and desorption studies of C.I. Reactive Black 5 on a novel photoassisted Fenton catalyst," *Dyes and Pigments* 75 (2007) 130-135
- [11] Y.S. Ho, C.C. Chiang, "Sorptions studies of acid dyes by mixed sorbents," *Adsorption* 7 (2001) 139–147.
- [12] Y. Vijaya, S. R. Popuri, V. M. Boddu, and A. Krishnaiah, "Modified chitosan and calcium alginate biopolymer sorbents for removal of nickel (II) through adsorption," *Carbohydr. Polym.* 72: 2008, 261-271.
- [13] F. A. A. Al-Rub, M. H. El-Naas, F. Benyahia and I. Ashour, "Biosorption of nickel on blank alginate beads, free and immobilized algal cells," *Process Biochem.* Volume 39: 2004, Issue 11, pp. 1767-1773.
- [14] A. M. Youssef, A. I. Ahmed, M. I. Amin and U. A. El-Banna, "Adsorption of lead by activated carbon developed from rice husk," *Desalin. Water Treat. Desalin. Water Treat.* Vol 54: 2015, Issue 6, pp. 1694-1707.
- [15] N. Sezgin, and N. Balkaya, "Adsorption of heavy metals from industrial wastewater by using polyacrylic acid hydrogel," *Desalin. Water Treat.* Vol 57: 2016, Issue 6, 2466-2480.
- [16] D. Liu, Y. Tao, K. Li and J. Yu, "Influence of the presence of three typical surfactants on the adsorption of nickel (II) to aerobic activated sludge," *Bioresour. Technol.* Vol 126: 2012, pp. 56-63.
- [17] Z. Liu, X. Chen, L. Zhou and P. Wei, "Development of a first-order kinetics-based model for the adsorption of nickel onto peat," *Min. Sci. Technol. China* Vol 19: 2009, Issue 2, 230-234.

**Bircan Köse**, received her PhD degree from the Department of Chemical Engineering, Atatürk University, Erzurum. She studied as a research assistant in the same university between 2006 and 2015. Her research interests include drying and dehydration of agricultural and horticultural crops adsorption on the biomaterials.

**Saliha Erentürk**, Dr. Erenturk is currently working as an Associate Professor with the Department of Chemical Engineering, Atatürk University, Erzurum, Turkey. Her recent works are focused on the drying of various materials and their mathematical modeling, heavy metal adsorption on the biomaterials, pectin extraction, biofuels production and improving the some properties of biodiesel.